

# Investigation of the selective catalytic reduction of NO by NH<sub>3</sub> on Fe-ZSM5 monolith catalysts

Oliver Kröcher<sup>a,\*</sup>, Mukundan Devadas<sup>a</sup>, Martin Elsener<sup>a</sup>, Alexander Wokaun<sup>a</sup>,  
Nicola Söger<sup>b</sup>, Marcus Pfeifer<sup>b</sup>, Yvonne Demel<sup>b</sup>, Lothar Mussmann<sup>b</sup>

<sup>a</sup> Paul Scherrer Institute, CH-5232 Villigen PSI, Switzerland

<sup>b</sup> Umicore AG & Co. KG, Automotive Catalysts, Rodenbacher Chaussee 4, D-63403 Hanau, Germany

Received 27 October 2005; received in revised form 20 March 2006; accepted 24 March 2006

Available online 2 May 2006

## Abstract


Fe-ZSM5 coated on cordierite monolith was investigated in the selective catalytic reduction (SCR) of NO with ammonia over a broad temperature range, applying simulated diesel exhaust gas conditions. The catalyst exhibited over 80% NO<sub>x</sub> reduction (DeNO<sub>x</sub>) from 400 to 650 °C at very good selectivity. The dosage of variable amounts of ammonia in the catalytic tests revealed that the SCR reaction is inhibited by ammonia. At very high temperatures DeNO<sub>x</sub> is reduced due to the selective catalytic oxidation (SCO) of ammonia to nitrogen and the oxidation to NO. Water-free experiments resulted in generally higher DeNO<sub>x</sub> values, which are explained by the inhibiting effect of water on the NO oxidation capability of Fe-ZSM5. The catalyst was stable upon thermal ageing and only 5–15% loss in DeNO<sub>x</sub> activity was observed after hydrothermal treatment. This loss in DeNO<sub>x</sub> is in parallel with a loss of ammonia storage capacity of the aged catalyst. Characterization by NH<sub>3</sub> TPD and MAS <sup>27</sup>Al NMR spectroscopy revealed dealumination of the zeolite by hydrothermal ageing, which reduces the Brønsted acidity of the catalyst.

© 2006 Elsevier B.V. All rights reserved.

**Keywords:** Fe-ZSM5; NO<sub>x</sub> conversion; Monolith; Stability; Urea SCR; Ammonia storage

## 1. Introduction

Iron zeolites of the type Fe-ZSM5 are successfully applied as catalysts for several chemical processes, e.g. the direct benzene to phenol hydroxylation [1,2], N<sub>2</sub>O decomposition [3,4] and NO<sub>x</sub> reduction in exhaust gases [5,6]. Among the latter diesel exhaust gases are especially challenging due to the changing temperatures, flows and concentrations. Currently, the selective catalytic reduction with urea (urea SCR) is judged to have the highest potential for coping the NO<sub>x</sub> emission problem of heavy-duty diesel engines [7–9]. Under the hydrothermal conditions in the exhaust pipe urea releases ammonia, which reacts with NO (>90% of NO<sub>x</sub> of an exhaust gas is formed by NO) according to the well-known standard SCR reaction [7]:



Fe-ZSM5 has been reported to be an active and selective catalyst for the SCR reaction in Refs. [5,6,10–13]. Despite of

the valuable information provided in these laboratory investigations, some aspects have not been considered sufficiently for a reliable evaluation of Fe-ZSM5 as SCR catalyst:

1. Water must be present in the basic feed in order to measure the actual performance of the catalyst and to investigate the “real” functionality of the catalyst. However, omitting water may be useful in additional experiments to reveal the reaction mechanism.
2. A good SCR catalyst combines a high NO<sub>x</sub> removal efficiency (DeNO<sub>x</sub>) with a high selectivity and low ammonia emissions after the catalyst. This means that suitable SCR catalysts must have acidic properties, which help to withdraw the ammonia in the catalyst and provide sufficiently high ammonia concentrations at the active SCR sites at already low ammonia concentrations. Excessive ammonia dosage only slightly increases the ammonia concentration at the active sites. Therefore, the DeNO<sub>x</sub> remains nearly constant and all excessive ammonia is emitted. By plotting DeNO<sub>x</sub> versus ammonia slip these important catalyst properties are combined in one graph, e.g.

\* Corresponding author. Tel.: +41 56 310 20 66; fax: +41 56 310 23 23.  
E-mail address: [oliver.kroecher@psi.ch](mailto:oliver.kroecher@psi.ch) (O. Kröcher).

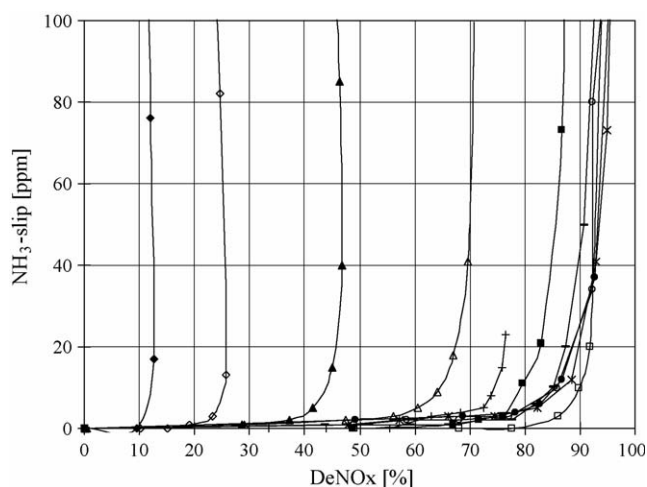


Fig. 1.  $\text{NH}_3$  slip vs.  $\text{DeNO}_x$  for the fresh Fe-ZSM5 monolith catalyst at (◆) 200 °C, (◇) 250 °C, (▲) 300 °C, (△) 350 °C, (■) 400 °C, (□) 450 °C, (●) 500 °C, (○) 550 °C, (×) 600 °C, (–) 650 °C and (+) 700 °C.

in Fig. 1. The almost rectangular curve shape is a consequence of the high SCR activities at low ammonia slip through the catalyst. Usually, ammonia emissions of about 10 ppm in average are regarded as harmless for automotive applications [14]. This necessitates a dosage control for adding the right amount of ammonia relating to the  $\text{NO}_x$  concentration and the activity of the catalyst. For catalyst screening experiments dosing a constant amount of ammonia and measuring the activity of the catalyst as a function of temperature is a valuable tool. However, with regard to dosage control in automotive applications a completed description of the catalyst performance is necessary. In our opinion, the temperature dependency of the catalyst activity is best expressed with respect to the allowable ammonia slip of 10 ppm independent of the ammonia to  $\text{NO}_x$  ratio dosed.

- Currently, a broad range of engine development strategies are followed, resulting in either low exhaust gas temperatures, e.g. for engines using excessive exhaust gas recycling (EGR), or very high exhaust gas temperatures, e.g. for engines without EGR but with hot diesel particulate filter (DPF) regeneration. Thus, to cover the maximum range of exhaust gas temperatures, the activity and selectivity of the catalysts should be checked from 150 to 700 °C.
- All above mentioned experimental studies report about Fe-ZSM5 powder catalysts, but monolith investigations are indispensable for gaining experimental data, which are representative of the situation in real world catalytic converters, i.e. low pressure drop, high geometric surface area and short diffusion distances [15].

In this paper we report about Fe-ZSM5 coated on a cordierite monolith in the selective catalytic reduction and selective catalytic oxidation reaction. The experiments were performed mainly in the presence of water over a broad temperature range considering the dependency of  $\text{DeNO}_x$  from the ammonia slip. Moreover, the stability as well as the ammonia storage capacity

## 2. Experimental

A commercially available Fe-ZSM5 powder was used as a model substance. The catalytic material was coated on a cordierite honeycomb of the size 4.66 in.  $\times$  4.66 in.  $\times$  3 in. with a cell density of 400 cpsi by Umicore automotive catalysts, Germany. For the catalytic investigation, the cordierite monolith was cut into pieces of the size 3.8 cm  $\times$  1.7 cm  $\times$  1.2 cm fitting to the sample holder of the tube reactor. Details about the plant set up are described in Ref. [14]. The gas hourly space velocity (GHSV = volumetric gas flow/coated monolith volume) was 52,000  $\text{h}^{-1}$ , which represents the flow conditions in SCR converters on board of diesel vehicles. For tests of the standard SCR reaction, the composition of diesel exhaust gas was approximated by a model feed gas containing 10%  $\text{O}_2$ , 5%  $\text{H}_2\text{O}$  1000 ppm of NO and balance  $\text{N}_2$ .  $\text{NH}_3$  was added in the range 100–2000 ppm. The selective catalytic oxidation (SCO) reaction of ammonia to nitrogen was tested with a model feed consisting of 10%  $\text{O}_2$ , 5%  $\text{H}_2\text{O}$  and 1000 ppm  $\text{NH}_3$  but no NO. Water was omitted for supplementing investigations. The concentrations of NO,  $\text{NO}_2$ ,  $\text{N}_2\text{O}$ ,  $\text{NH}_3$  and  $\text{H}_2\text{O}$  in the gas phase were analysed by HR-FTIR spectroscopy (Nicolet Magna IR 560, OMNIC QuantPad software) equipped with a heated multiple pass gas cell.

The thermal and hydrothermal stability of the Fe-ZSM5 catalyst coated on cordierite was tested by ageing at 650 °C in the presence of 10% oxygen in nitrogen for 50 h (denoted as “dry aged”) and by ageing at 650 °C in 10% water and 10% oxygen in nitrogen for 50 h (denoted as “wet aged”), respectively.

The ammonia adsorption capacities of the fresh, the dry aged and the wet aged monolith catalysts were measured at six different temperatures between 200 and 450 °C by two different methods. (a) Thermal desorption: 1000 ppm ammonia was adsorbed on the fresh Fe-ZSM5 monolith catalyst at a fixed temperature in 10%  $\text{O}_2$ , 5%  $\text{H}_2\text{O}$  and balance  $\text{N}_2$ . The GHSV was maintained at 52,000  $\text{h}^{-1}$ . In the desorption procedure, part of the ammonia was removed by purging the sample at the adsorption temperature with pure  $\text{N}_2$ , followed by increasing the temperature up to 450 °C in order to complete the ammonia desorption. (b) Combination of physical desorption and reaction of pre-adsorbed ammonia by NO according to the method of Kleemann et al. [16]: first, ammonia was adsorbed using a nitrogen gas flow containing 10%  $\text{O}_2$ , 5%  $\text{H}_2\text{O}$  and 1000 ppm of  $\text{NH}_3$ , at a fixed temperature until this concentration was also reached at the catalyst outlet. Subsequently, the chemically accessible ammonia was removed by stopping the ammonia dosage and simultaneously dosing 10%  $\text{O}_2$ , 5%  $\text{H}_2\text{O}$  and 1000 ppm of NO at the same temperature until the NO consumption ceased. The physically desorbed ammonia was measured in parallel. Oxygen and water were always added in order to obtain ammonia storage capacities, being representative for diesel exhaust gas conditions.

Powder samples of the Fe-ZSM5 catalyst were used for characterization. Temperature programmed desorption of ammonia ( $\text{NH}_3$  TPD) was carried out in a TPD/TPR 2900

conductivity detector. Fifty milligram of sample were degassed at 550 °C for 1 h in a He flow and cooled down to 100 °C. At this temperature adsorption of NH<sub>3</sub> took place until saturation. Afterwards, the catalyst was flushed with He for 30 min. TPD measurements were performed from 100 to 650 °C with a heating rate of 20 °C/min, with He as carrier gas.

<sup>27</sup>Al MAS NMR spectra were obtained on a Bruker Ultrashield 500 spectrometer at a magnetic field of 11.7 T equipped with a 4 mm MAS head probe. The aluminium resonance frequency at this field is 130 MHz. The sample rotation speed was 12.5 kHz. The <sup>27</sup>Al chemical shifts were referenced to a saturated Al(NO<sub>3</sub>)<sub>3</sub> solution. To obtain NMR spectra as quantitatively as possible in the presence of a heterogeneous distribution of quadrupolar coupling constants, the <sup>27</sup>Al nuclei were excited with a single 20° pulse of 1 μs. Excitation pulses longer than 3 μs were seen to overemphasize the extra-framework aluminium signal intensity relative to the framework aluminium signal. The relaxation delay between the scans was set to 1 s. No saturation effects were observed in the spectrum for relaxation delays longer than 0.5 s.

### 3. Results and discussion

#### 3.1. Catalytic performance of Fe-ZSM5 monolith catalysts

##### 3.1.1. Standard-SCR over Fe-ZSM5

From Fig. 1, the high SCR activity of Fe-ZSM5 is clearly discernible, especially at temperatures above 350 °C. In accordance with the expected behaviour of a suitable SCR catalyst nearly all ammonia dosed goes into the SCR reaction, limited either by the activity of the catalyst at a given temperature or the stoichiometry of the SCR reaction. All additional ammonia causes an only marginal increase of the DeNO<sub>x</sub>. However, having a closer look at the ammonia slip at lower and intermediate temperatures up to 350 °C reveals an interesting behaviour. The steep part of the curves are slightly bent backward, indicating that the NO<sub>x</sub> conversion first increases as expected but then decreases again if ammonia is overdosed and ammonia slip is forced. Obviously, the SCR reaction is inhibited by ammonia. This effect is more pronounced in Fig. 2, where DeNO<sub>x</sub> values are plotted against the stoichiometric ratio  $\alpha = \text{NH}_{3,\text{in}}/\text{NO}_{x,\text{in}}$  for different temperatures in the range 200–500 °C. These results suggest that the inhibition effect of ammonia could be due to competitive adsorption of ammonia and NO on the active sites. In fact, Eng and Bartholomew [17] and Stevenson et al. [18] observed a similar inhibition by ammonia on H-ZSM5, which was attributed to a competitive adsorption of ammonia and NO.

Fig. 3 illustrates the differences between the DeNO<sub>x</sub> at 10 ppm NH<sub>3</sub> slip and the maximum DeNO<sub>x</sub>, plotted versus temperature in the range 200–700 °C. In accordance with Fig. 2, the difference between the maximum DeNO<sub>x</sub> and DeNO<sub>x</sub> at 10 ppm ammonia slip decreases for lower temperatures due to the ammonia inhibition effect, which prevents that the catalyst activity is increased by adding ammonia in excess. In this temperature range DeNO<sub>x</sub> is rather limited by the reaction

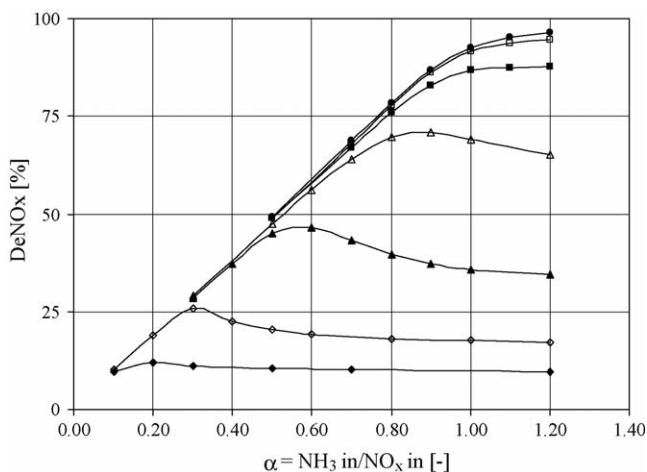


Fig. 2. DeNO<sub>x</sub> vs. stoichiometric factor  $\alpha$  for the fresh Fe-ZSM5 monolith catalyst at (◆) 200 °C, (◇) 250 °C, (▲) 300 °C, (△) 350 °C, (■) 400 °C, (□) 450 °C and (●) 500 °C.

200 to 600 °C, reaching >90% for  $T > 450$  °C. It decreases at temperatures beyond 600 °C. However, at 700 °C still around 80% of conversion was achieved.


##### 3.1.2. Possible side-reactions during standard-SCR over Fe-ZSM5

Generally, DeNO<sub>x</sub> is expected to be limited by the catalyst activity at lower temperatures, the stoichiometry of the SCR reaction at intermediate temperatures and by the catalyst selectivity at high temperatures. With increasing temperatures different side-reactions are conceivable producing N<sub>2</sub>O and NO<sub>x</sub> as well as increased amounts of nitrogen [19].

For the production of N<sub>2</sub>O the direct oxidation of ammonia,




and the reaction of ammonia with NO<sub>2</sub> are discussed [19]:



Other potential side-reactions of the SCR process are the selective catalytic oxidation of ammonia to nitrogen (SCO),



and the oxidation of ammonia to NO,



which itself may be further oxidized to NO<sub>2</sub>.

##### 3.1.3. N<sub>2</sub>O formation

Fig. 3 clearly shows that only negligible amounts of N<sub>2</sub>O (~3 ppm) were formed during standard-SCR between 250 and 400 °C and that no N<sub>2</sub>O was formed beyond 450 °C. This makes reaction (2) very unlikely, which is expected to produce increasingly amounts of N<sub>2</sub>O formation at higher temperatures. The reaction of ammonia with oxygen over Fe-ZSM5 was investigated without the influence of the SCR reaction by dosing ammonia without NO (Fig. 4a). No N<sub>2</sub>O was formed at any temperature, ruling out the relevance of reaction (2) for the



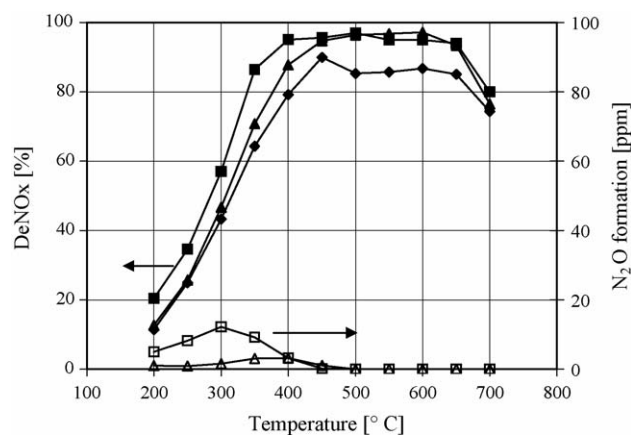


Fig. 3. DeNOx vs. temperature for the fresh Fe-ZSM monolith (◆) at 10 ppm NH<sub>3</sub> slip with water in feed, (▲) at maximum conversion with water in feed and (■) at 10 ppm NH<sub>3</sub> slip without water. (△) N<sub>2</sub>O formation at 10 ppm NH<sub>3</sub> slip with water in feed and (□) at 10 ppm NH<sub>3</sub> slip without water.

reaction equation the N<sub>2</sub>O formation should be independent of the NO<sub>2</sub> content in the feed. However, experiments with increasing NO<sub>2</sub> fractions in the feed, which will be subject of another publication, clearly showed the dependency of the N<sub>2</sub>O emissions on the NO<sub>2</sub> concentration in the gas feed at 250–400 °C. This proves the relevance of reaction (3) for the

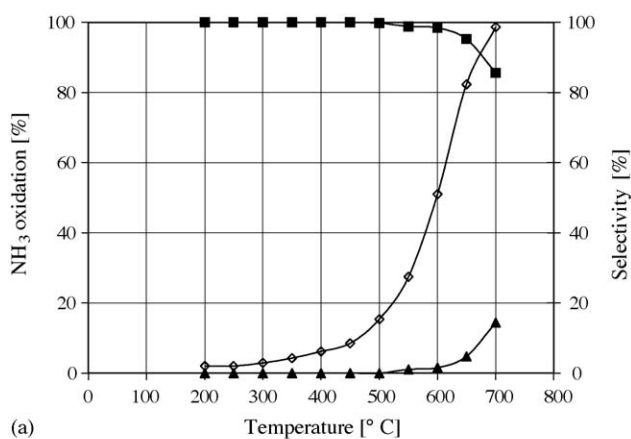

(a)

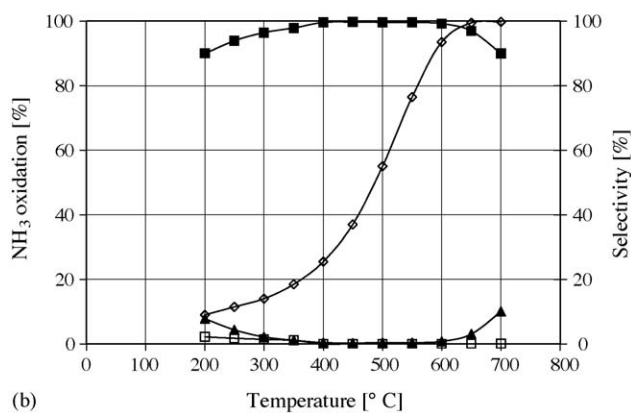


(b)

Fig. 4. SCO properties of the fresh Fe-ZSM5 monolith vs. temperature (a) in the presence of water and (b) without water. (◇) NH<sub>3</sub> oxidized, (▲) selectivity

formation of N<sub>2</sub>O on Fe-ZSM5. However, having a closer look at the underlying chemistry, the contribution of reaction (2) cannot be strictly ruled out, as N<sub>2</sub>O might be formed as a short living intermediate at higher temperatures. In fact, Fe-ZSM5 shows strongly increasing N<sub>2</sub>O decomposition activity at  $T > 400$  °C



and N<sub>2</sub>O SCR activity at  $T > 350$  °C [20]



explaining the general absence of N<sub>2</sub>O at higher temperatures independent of the reaction conditions or the feed composition.

### 3.1.4. SCO reaction and NO formation

The investigation of the ammonia oxidation over Fe-ZSM5 showed that ammonia conversion strongly increases with temperatures (Fig. 4a). Around 50% of the ammonia was oxidized at  $T = 600$  °C and nearly 100% at 700 °C. The selectivity towards N<sub>2</sub> was almost 100% till 600 °C, but beyond 600 °C the selectivity towards nitrogen decreased accompanied with an increase in NO formation. The formation of NO beside the main product N<sub>2</sub> in the ammonia oxidation experiment gives occasion to the assumption that during SCR over Fe-ZSM5 NO is not only consumed but also produced on the catalyst by reaction of ammonia with oxygen. This NO cannot be distinguished from the NO in the feed and, especially, if it is formed at the catalyst entrance it may also react downstream in the standard SCR reaction (1). Based on the observed products, it not possible to decide, if the oxidation of ammonia to nitrogen is a straightforward reaction or if it proceeds via NO as intermediate.

### 3.1.5. NO<sub>2</sub> formation

Fe-ZSM5 has a distinct NO oxidation capability as shown in Fig. 5. The NO<sub>2</sub> fraction increases with temperature as expected, but decreases again at higher temperatures due to the thermodynamic equilibrium between NO and NO<sub>2</sub> lying on the side of NO. NO<sub>2</sub> is essential for SCR activity of ZSM5-


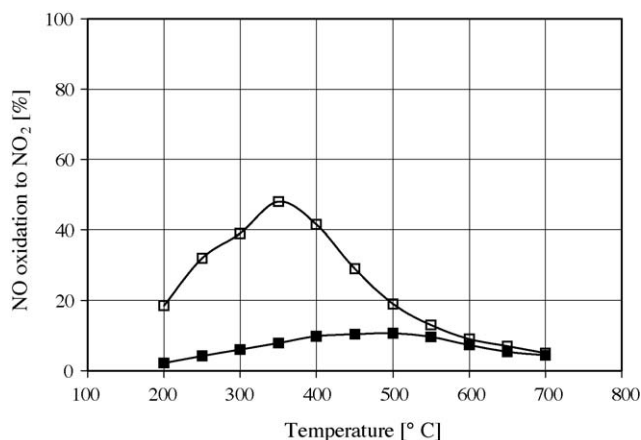


Fig. 5. NO oxidation to NO<sub>2</sub> for the fresh Fe-ZSM monolith (■) with water in

based catalysts [21], but, as the  $\text{NO}_2$  formed from  $\text{NO}$  is not observed under standard-SCR conditions (Fig. 3) it may be concluded that it is only a short living intermediate, which is immediately consumed. The decisive function of  $\text{NO}_2$  on the SCR reaction over Fe-ZSM5 was confirmed by adding  $\text{NO}_2$  to the feed, which drastically increased the DeNO<sub>x</sub> values up to  $\text{NO}_2/\text{NO}_x = 0.5$ , especially at low temperatures [22]. The SCR reaction involving  $\text{NO}_2$  is called fast-SCR [19] and is described by reaction equation (9). It may be regarded as the *actual* and *general* SCR stoichiometry over zeolite based catalysts, because either  $\text{NO}_2$  in the feed or the presence of an oxidation functionality in the zeolite for the oxidation of  $\text{NO}$  to  $\text{NO}_2$  is a pre-requisite for SCR activity:



### 3.1.6. SCR stoichiometry

The problem for the investigation of the SCR reaction is, that all reactions end up directly or via intermediates in nitrogen or  $\text{NO}$ , which cannot be distinguished from the feed components. Moreover, nitrogen cannot be detected by infrared spectroscopy. However, the contribution of all these side-reactions results in an increased consumption of ammonia relatively to the 1:1 stoichiometry of the SCR reaction. This excess consumption is derived from the curves in Fig. 6, showing the ratio of consumed ammonia to consumed  $\text{NO}_x$  versus the ratio of dosed ammonia to dosed  $\text{NO}_x$  at 200–700 °C, which is a direct scale for the compliance of the SCR stoichiometry. The values of 1–1.1 between 200 and 600 °C clearly demonstrate that Fe-ZSM5 follows the ideal SCR stoichiometry over a broad temperature range and that a maximum of 10% ammonia is consumed by ammonia oxidation. However, at 700 °C, values of about 1.5–1.7 were observed, indicating that the catalyst consumed an increasing part of ammonia mainly due to the oxidation to nitrogen at very high temperatures.

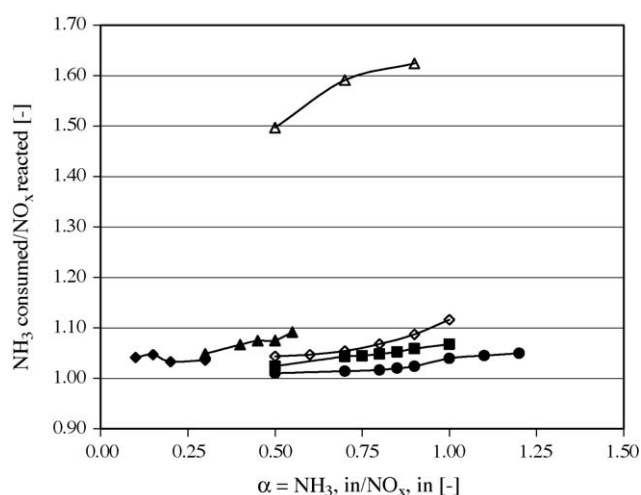


Fig. 6. Observed ammonia to  $\text{NO}_x$  stoichiometry vs. dosed ammonia to  $\text{NO}_x$  ratio at (◆) 200 °C, (▲) 300 °C, (■) 400 °C, (●) 500 °C, (◇) 600 °C and (△) 700 °C.

### 3.1.7. Water-free experiments

In order to obtain a clearer picture of the functionality of the catalyst also water-free experiments have been performed. From Fig. 3 it is clearly discernible that Fe-ZSM5 shows a generally higher DeNO<sub>x</sub> activity if water is omitted. However, also much more  $\text{N}_2\text{O}$  is formed reaching a maximum of 12 ppm at intermediate temperatures. As stated above this side-product is typically formed in larger amounts at intermediate temperatures if  $\text{NO}_2$  is present in the gas feed [22]. It is obvious from Fig. 5 that also much more  $\text{NO}_2$  is formed under water-free conditions than with water in the feed. Thus, the increase in  $\text{N}_2\text{O}$  formation under water-free conditions is easily explained by the elevated concentration of  $\text{NO}_2$  on the catalyst.

The higher oxidation capability of the catalyst under water free conditions, observable from the elevated  $\text{NO}_2$  concentrations in Fig. 5, is also apparent in the investigation of the ammonia oxidation without water as shown in Fig. 4b. By omitting the water, elevated  $\text{NH}_3$  conversions are observed over the whole temperature range. At lower temperatures the occurrence of  $\text{NO}$  and  $\text{N}_2\text{O}$  is remarkable, which was not observed in the presence of water. Apparently, the ammonia oxidation to  $\text{NO}$  is promoted more than the following SCR reaction, resulting in the production of  $\text{NO}$  beside the main product  $\text{N}_2$ . With increasing temperature  $\text{NO}$  decreases as the SCR reaction accelerates faster than the ammonia oxidation.

Long and Yang [23] investigated the SCO reaction over powdered iron zeolites at temperatures up to 450 °C. They also found, that under water-free conditions the selectivity of the SCO reaction to nitrogen increases with temperature at the expense of a decrease in  $\text{NO}$  formation. This was explained by  $\text{NO}$  being the intermediate of the SCO reaction, which is reduced to nitrogen by  $\text{NH}_3$  in the SCR reaction.

The formation of  $\text{N}_2\text{O}$  seems to be coupled to the presence of gas phase  $\text{NO}$ . Due to the high oxidation capability of Fe-ZSM5, it is very likely, that part of the  $\text{NO}$  formed is further oxidized to  $\text{NO}_2$  due to the strong oxidizing properties of the catalyst under water-free conditions. The  $\text{NO}_2$ , however, is not observable, as it is rapidly converted to nitrogen according to the “fast-SCR” reaction already at 200 °C [22]. Thus, the observed formation of  $\text{N}_2\text{O}$  would be a side-product of the “fast-SCR” reaction at low temperatures.

### 3.2. Stability of Fe-ZSM5 monolith catalysts

Stability under real-world conditions is an important parameter for the assessment of the suitability of a catalyst. Therefore, Long and Yang [24] investigated the durability of Fe-ZSM5 powder catalysts, aged in  $\text{SO}_2$  and  $\text{H}_2\text{O}$  for 60 h at 350 °C. They observed a 20% loss in  $\text{NO}$  conversion. Feng and Hall [25] studied the durability of the Fe-ZSM5 powder catalyst for a period of 2500 h at 500 °C. They observed a minimal loss in  $\text{NO}$  activity in a simulated exhaust gas stream. We checked both the thermal and hydrothermal stability of Fe-ZSM5, but coated on the cordierite honeycomb. Fig. 7a compares the  $\text{NO}_x$  conversion at 10 ppm ammonia slip versus reaction temperature of the aged catalysts with the results of the fresh catalyst

# Explore Litigation Insights

Docket Alarm provides insights to develop a more informed litigation strategy and the peace of mind of knowing you're on top of things.

## Real-Time Litigation Alerts



Keep your litigation team up-to-date with **real-time alerts** and advanced team management tools built for the enterprise, all while greatly reducing PACER spend.

Our comprehensive service means we can handle Federal, State, and Administrative courts across the country.

## Advanced Docket Research



With over 230 million records, Docket Alarm's cloud-native docket research platform finds what other services can't. Coverage includes Federal, State, plus PTAB, TTAB, ITC and NLRB decisions, all in one place.

Identify arguments that have been successful in the past with full text, pinpoint searching. Link to case law cited within any court document via Fastcase.

## Analytics At Your Fingertips



Learn what happened the last time a particular judge, opposing counsel or company faced cases similar to yours.

Advanced out-of-the-box PTAB and TTAB analytics are always at your fingertips.

## API

Docket Alarm offers a powerful API (application programming interface) to developers that want to integrate case filings into their apps.

## LAW FIRMS

Build custom dashboards for your attorneys and clients with live data direct from the court.

Automate many repetitive legal tasks like conflict checks, document management, and marketing.

## FINANCIAL INSTITUTIONS

Litigation and bankruptcy checks for companies and debtors.

## E-DISCOVERY AND LEGAL VENDORS

Sync your system to PACER to automate legal marketing.