


CRC Handbook of Chemistry and Physics

A Ready-Reference Book of Chemical and Physical Data

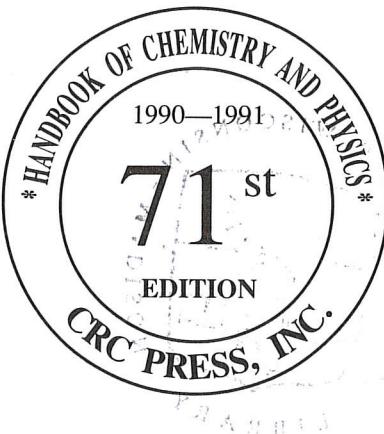

Editor-in-Chief

David R. Lide, Ph.D.



CRC Press
Boca Raton Ann Arbor Boston



©1974, 1975, 1976, 1977, 1978, 1979, 1980, 1981, 1982, 1983, 1984, 1985, 1986, 1987, 1988, 1989, 1990 by CRC Press, Inc.

©1964, 1965, 1966, 1967, 1968, 1969, 1970, 1971, 1972, 1973 by THE CHEMICAL RUBBER CO.

Copyright 1918, 1920 by The Chemical Rubber Company (Copyright renewed 1946, 1948 by The Chemical Rubber Publishing Company)

Copyright 1922 (Copyright renewed 1950), 1925 (Copyright renewed 1953), 1926 (Copyright renewed 1954), 1927 (Copyright renewed 1955), 1929 (Copyright renewed 1957), 1936, 1937 (Copyright renewed 1965 by The Chemical Rubber Co.), 1939, 1940 (Copyright renewed 1968 by the Chemical Rubber Co.), 1941 (Copyright renewed 1969 by The Chemical Rubber Co.), 1942 (Copyright renewed 1970 by The Chemical Rubber Co.), 1943 (Copyright renewed 1971 by The Chemical Rubber Co.), 1944 (Copyright renewed 1972 by The Chemical Rubber Co.), 1945 (Copyright renewed 1973 by The Chemical Rubber Co.), 1947, 1949, 1950, 1951, 1952 (Copyright renewed 1980 by CRC Press, Inc.), 1953 (Copyright renewed 1981a by CRC Press, Inc.), 1954 (Copyright renewed 1982 by CRC Press, Inc.), 1955 (Copyright renewed 1983 by CRC Press, Inc.), 1956 by Chemical Rubber Publishing Company

©1957, 1958, 1959, 1960, 1962 by Chemical Rubber Publishing Company

All Rights Reserved
Library of Congress Card No. 13-11056
PRINTED IN U.S.A.

ISBN-0-8493-0471-7

+AD3276

JUL 16 1990

~~REFERENCE COLLECTION
MEMORIAL LIBRARY~~
**REFERENCE COLLECTION
MEMORIAL LIBRARY**

**ATOMIC WEIGHTS, MELTING AND BOILING POINTS OF CIRCULATING
THE ELEMENTS (CONTINUED)**

Name	Symbol	Atomic number	Atomic weight	Footnotes	Melting point (°C)	Boiling point (°C)
Radium	Ra	88	226.025		700	1140
Radon	Rn	86	(222)		-71	-61.8
Rhenium	Re	75	186.207(1)		3180	5627 (est.)
Rhodium	Rh	45	102.90550(3)		1965 ± 3	3727 ± 100
Rubidium	Rb	37	85.4678(3)	g	38.89	686
Ruthenium	Ru	44	101.07(2)	g	2310	3900
Samarium	Sm	62	150.36(3)	g	1074	1794
Scandium	Sc	21	44.955910(9)		1541	2836
Selenium	Se	34	78.96(3)		217	684.9 ± 1.0
Silicon	Si	14	28.0855(3)		1410	2355
Silver (Argentum)	Ag	47	107.8682(2)	g	961.93	2212
Sodium (Natrium)	Na	11	22.989768(6)		97.81 ± 0.03	882.9
Strontium	Sr	38	87.62(1)	g	769	1384
Sulfur	S	16	32.066(6)	r	112.8	444.674
Tantalum	Ta	73	180.9479(1)		2996	5425 ± 100
Technetium	Tc	43	(98)		2172	4877
Tellurium	Te	52	127.60(3)	g	449.5 ± 0.3	989.8 ± 3.8
Terbium	Tb	65	158.92534(3)		1356	3230
Thallium	Tl	81	204.3833(2)		303.5	1457 ± 10
Thorium	Th	90	232.0381(1)	g, L	1750	3800 (approx.)
Thulium	Tm	69	168.93421(3)		1545	1950
Tin (Stannum)	Sn	50	118.710(7)		231.9681	2270
Titanium	Ti	22	47.88(3)		1660 ± 10	3287
Tungsten (Wolfram)	W	74	183.85(3)		3410 ± 20	5660
Unnilhexium	(Unh)	106	(263)			
Unnilpentium	(Unp)	105	(262)			
Unnilquadium	(Unq)	104	(261)			
Unnilseptium	(Uns)	107	(262)			
Uranium	U	92	238.0289(1)	g, m	1132 ± 0.8	3818
Vanadium	V	23	50.9415(1)		1890 ± 10	3380
Wolfram (see Tungsten)						
Xenon	Xe	54	131.29(2)	g, m	-111.9	-107.1 ± 3
Ytterbium	Yb	70	173.04(3)		819	1196
Yttrium	Y	39	88.90585(2)		1552	5338
Zinc	Zn	30	65.39(2)		419.58	907
Zirconium	Zr	40	91.224(2)	g	1852 ± 2	4377

- g geological exceptional specimens are known in which the element has an isotopic composition outside the limits for normal material. The difference between the atomic weight of the element in such specimens and that given in the Table may exceed considerably the implied uncertainty.
- m modified isotopic compositions may be found in commercially available material because it has been subjected to an undisclosed or inadvertent isotopic separation. Substantial deviations in atomic weight of the element from that given in the Table can occur.
- r range in isotopic composition of normal terrestrial material prevents a more precise atomic weight being given; the tabulated A_r(E) value should be applicable to any normal material.
- t Triple point; (graphite-liquid-gas), 3627 ± 50°C at a pressure of 10.1 MPa and (graphite-diamond-liquid), 3830 to 3930°C at a pressure of 12 to 13 GPa.
- L Longest half-life isotope mass is chosen for the tabulated Ar (E) value.

MEMORIAL LIBRARY

TRANSFERRER
TO THE STACKS

SPECIFIC HEAT AND ENTHALPY OF SOME SOLIDS AT LOW TEMPERATURES

R. J. Corruccini and J. J. Gniewek

For a more extensive listing of data one is referred to N.B.S. Monograph 21 (1960)
 $\text{Joules/g} \times 453.6 = \text{joules/lb} \times 0.239 = \text{cal/g} \times 0.4299 = \text{Btu/lb}$

Metals

T °K	Aluminum		Beryllium		Bismuth		Cadmium	
	C _p jg ⁻¹ deg ⁻¹ K	H — H ₀ jg ⁻¹	C _p jg ⁻¹ deg ⁻¹ K	H — H ₀ jg ⁻¹	C _p jg ⁻¹ deg ⁻¹ K	H — H ₀ jg ⁻¹	C _p jg ⁻¹ deg ⁻¹ K	H — H ₀ jg ⁻¹
1	0.00010 ^a	—	—	—	—	—	—	—
1	0.000051	0.000025	0.000025	0.000013	0.00000598	0.00000158	0.000008	0.000003
2	0.000108	0.000105	0.000051	0.000051	0.0000461	0.0000233	0.000033	0.000022
3	0.000176	0.000246	0.000079	0.000116	0.000170	0.000123	0.000090	0.000082
4	0.000261	0.000463	0.000109	0.000209	0.000493	0.000432	0.00021	0.00022
6	0.00050	0.00121	0.000180	0.000496	0.00214	0.00288	0.00130	0.0015
8	0.00088	0.0026	0.000271	0.000944	0.00547	0.0102	0.0043	0.0070
10	0.0014	0.0049	0.000389	0.00160	0.0104	0.0259	0.0080	0.109
15	0.0040	0.018	0.000842	0.00457	0.0238	0.111	0.025	0.102
20	0.0089	0.048	0.00161	0.0105	0.0363	0.262	0.046	0.28
25	0.0175	0.112	0.00279	0.0212	0.0477	0.472	0.066	0.56
30	0.0315	0.232	0.00450	0.0392	0.0572	0.734	0.086	0.94
35	0.0515	0.436	—	—	—	—	—	—
40	0.0775	0.755	0.00996	0.109	0.0727	1.38	0.117	1.96
50	0.142	1.85	0.0192	0.253	0.0846	2.17	0.141	3.26
60	0.214	3.64	0.0341	0.523	0.0935	3.06	0.159	4.76
70	0.287	6.15	0.0562	0.971	0.100	4.03	0.172	6.43
80	0.357	9.37	0.0906	1.69	0.105	5.05	0.182	8.20
90	0.422	13.25	0.139	2.82	0.108	6.12	0.190	10.1
100	0.481	17.76	0.199	4.51	0.111	7.21	0.196	12.0

T °K	Chromium		Copper		Germanium ^b		Gold	
	C _p jg ⁻¹ deg ⁻¹ K	H — H ₀ jg ⁻¹	C _p jg ⁻¹ deg ⁻¹ K	H — H ₀ jg ⁻¹	C _p jg ⁻¹ deg ⁻¹ K	H — H ₀ jg ⁻¹	C _p jg ⁻¹ deg ⁻¹ K	H — H ₀ jg ⁻¹
1	0.0000285	0.0000142	0.000012	0.00006	0.00000528	0.000000132	0.000006	0.000002
2	0.000058	0.0000573	0.000028	0.000025	0.0000423	0.00000211	0.000025	0.000016
3	0.000089	0.000131	0.000053	0.000064	0.0000144	0.0000107	0.000070	0.000061
4	0.00014	0.000237	0.000091	0.00013	0.0000344	0.0000343	0.00016	0.00017
6	0.000206	0.000567	0.00023	0.00044	0.000125	0.000179	0.00050	0.00078
6	0.000206	0.000567	0.00023	0.00044	0.000125	0.000179	0.00050	0.00078
8	0.000312	0.00107	0.00047	0.00112	0.00035	0.000612	0.0012	0.0024
10	0.000451	0.00182	0.00086	0.0024	0.000813	0.00169	0.0022	0.0056
15	0.00102	0.00528	0.0027	0.0107	0.00445	0.0136	0.0074	0.028
20	0.00210	0.0128	0.0077	0.034	0.0125	0.0540	0.0159	0.086
25	0.00392	0.0274	0.016	0.090	0.0240	0.145	0.0263	0.191
30	0.00683	0.0532	0.027	0.195	0.0366	0.296	0.0371	0.349
40	0.0171	0.163	0.060	0.61	0.0617	0.786	0.0572	0.821
50	0.0358	0.421	0.099	1.40	0.0858	1.52	0.0726	1.47
60	0.0621	0.904	0.137	2.58	0.108	2.50	0.0842	2.25
70	0.093	1.68	0.173	4.13	0.131	3.70	0.0928	3.14
80	0.127	2.77	0.205	6.02	0.153	5.12	0.0992	4.10
90	0.161	4.21	0.232	8.22	0.173	6.74	0.1043	5.12
100	0.193	5.98	0.254	10.6	0.191	8.55	0.1083	6.18

T °K	Indium		α -Iron ^c		γ -Iron ^d		Lead	
	C _p jg ⁻¹ deg ⁻¹ K	H — H ₀ jg ⁻¹	C _p jg ⁻¹ deg ⁻¹ K	H — H ₀ jg ⁻¹	C _p jg ⁻¹ deg ⁻¹ K	H — H ₀ jg ⁻¹	C _p jg ⁻¹ deg ⁻¹ K	H — H ₀ jg ⁻¹
1	0.000029	0.000011	0.000090	0.000045	—	—	0.000026	0.000010
1	0.000019 ^a	0.000006 ^a	—	—	—	—	0.000012 ^a	0.000003 ^a
2	0.000138	0.000085	0.000183	0.000181	—	—	0.00012	0.00007
2	0.000141 ^a	0.000073 ^a	—	—	—	—	0.00009 ^a	0.00005 ^a
3	0.000410	0.000341	0.000279	0.000412	—	—	0.00033	0.00023 ^a
3	0.000464 ^a	0.000357 ^a	—	—	—	—	0.00031 ^a	—
3.40 ^e	0.000584	0.000537	—	—	—	—	—	—
3.40	0.000669 ^a	0.000581 ^a	—	—	—	—	—	—
4	0.00095	0.00099	0.000382	0.000742	—	—	0.0007	0.0008
4	—	—	—	—	—	—	0.0007 ^a	0.0007 ^a
5	—	—	—	—	—	—	0.0015	0.0018
5	—	—	—	—	—	—	0.0015 ^a	0.0018 ^a
6	0.00359	0.00520	0.000615	0.00173	—	—	0.0029	0.0039
6	—	—	—	—	—	—	0.0030 ^a	0.0040 ^a
7	—	—	—	—	—	—	0.0048	0.008

SPECIFIC HEAT AND ENTHALPY OF SOME SOLIDS AT LOW TEMPERATURES (continued)

Chromium			Copper			Germanium ^b			Gold		
T °K	C _p Jg ⁻¹ deg ⁻¹ K	H — H ₀ Jg ⁻¹	C _p Jg ⁻¹ deg ⁻¹ K	H — H ₀ Jg ⁻¹	C _p g ⁻¹ deg ⁻¹ K	H — H ₀ Jg ⁻¹	C _p Jg ⁻¹ deg ⁻¹ K	H — H ₀ Jg ⁻¹	C _p Jg ⁻¹ deg ⁻¹ K	H — H ₀ Jg ⁻¹	
7	—	—	—	—	—	—	—	—	0.0050 ^a	0.008 ^a	
8	0.00855	0.0170	0.00090	0.003233	—	—	—	—	0.0073	0.014	
10	0.0155	0.0408	0.00124	0.00537	—	—	—	—	0.0137	0.034	
15	0.036	0.170	0.00249	0.0145	—	—	—	—	0.0335	0.150	
20	0.0608	0.413	0.0045	0.0316	0.007	0	0.0531	0.368	—	—	
25	0.0857	0.778	0.0075	0.061	—	—	—	—	0.0681	0.672	
30	0.108	1.265	0.0124	0.110	0.016	0.11	0.0796	1.042	—	—	
40	0.141	2.52	0.029	0.31	0.041	0.39	0.0944	1.920	—	—	
50	0.162	4.04	0.055	0.73	0.090	1.0 ²	0.103	2.91	—	—	
60	0.176	5.73	0.087	1.43	0.13 ²	2.1 ⁶	0.108	3.97	—	—	
70	0.186	7.53	0.121	2.46	0.18 ⁰	3.7 ⁵	0.112	5.07	—	—	
80	0.193	9.42	0.154	3.84	0.21 ⁸	5.74 ⁴	0.114	6.20	—	—	
90	0.198	11.38	0.186	5.55	0.25 ⁵	8.1 ¹	0.116	7.35	—	—	
100	0.203	13.39	0.216	7.56	0.28 ⁸	10 ⁸	0.118	853	—	—	
Molybdenum			Nickel			Palladium					
T °K	C _p Jg ⁻¹ deg ⁻¹ K	H — H ₀ Jgum ¹	C _p Jg ⁻¹ deg ⁻¹ K	H — H ₀ Jg ⁻¹	C _p Jg ⁻¹ deg ⁻¹ K	H — H ₀ Jg ⁻¹	C _p Jg ⁻¹ deg ⁻¹ K	H — H ₀ Jg ⁻¹			
1	0.0000229	0.0000105	0.000120	0.000060	0.000099	0.0000493	—	—	—	—	—
2	0.0000472	0.0000445	0.000242	0.000241	0.000203	0.000200	—	—	—	—	—
3	—	—	—	—	—	—	—	—	—	—	—
3	0.0000745	0.000105	0.000369	0.000546	0.000318	0.000459	—	—	—	—	—
3	—	—	—	—	—	—	—	—	—	—	—
4	0.000106	0.000194	0.000503	0.00098	0.000447	0.000840	—	—	—	—	—
4	—	—	—	—	—	—	—	—	—	—	—
5	—	—	—	—	—	—	—	—	—	—	—
5	—	—	—	—	—	—	—	—	—	—	—
6	0.000191	0.000484	0.00082	0.00228	0.000891	0.00231	—	—	—	—	—
6	—	—	—	—	—	—	—	—	—	—	—
7	—	—	—	—	—	—	—	—	—	—	—
7	—	—	—	—	—	—	—	—	—	—	—
8	0.000317	0.000981	0.00119	0.00428	0.00141	0.00460	—	—	—	—	—
8	—	—	—	—	—	—	—	—	—	—	—
9	—	—	—	—	—	—	—	—	—	—	—
9	—	—	—	—	—	—	—	—	—	—	—
10	0.000498	0.00178	0.00162	0.0071	0.00210	0.00807	—	—	—	—	—
15	0.00131	0.00610	0.0031	0.0185	0.00471	0.0245	—	—	—	—	—
20	0.00287	0.0161	0.0058	0.041	0.00922	0.0586	—	—	—	—	—
25	0.00577	0.0374	0.0101	0.079	0.0160	0.120	—	—	—	—	—
30	0.00960	0.0729	0.0167	0.145	0.0258	0.223	—	—	—	—	—
40	0.0236	0.232	0.0381	0.413	0.0507	0.600	—	—	—	—	—
50	0.0410	0.554	0.0682	0.937	0.0777	1.24	—	—	—	—	—
60	0.0619	1.07	0.103	1.79	0.101	2.14	—	—	—	—	—
70	0.0838	1.80	0.139	3.00	0.122	3.26	—	—	—	—	—
80	0.104	2.74	0.173	4.56	0.139	4.56	—	—	—	—	—
90	0.123	3.88	0.204	6.45	0.154	6.03	—	—	—	—	—
100	0.139	5.20	0.232	8.63	0.167	7.63	—	—	—	—	—
Platinum			Rhodium			Silicon ¹			Silver		
T °K	C _p Jg ⁻¹ deg ⁻¹ K	H — H ₀ Jg ⁻¹	C _p Jg ⁻¹ deg ⁻¹ K	H — H ₀ Jg ⁻¹	C _p Jg ⁻¹ deg ⁻¹ K	H — H ₀ Jg ⁻¹	C _p Jg ⁻¹ deg ⁻¹ K	H — H ₀ Jg ⁻¹	C _p Jg ⁻¹ deg ⁻¹ K	H — H ₀ Jg ⁻¹	
1	0.000035	0.0000175	0.00048	0.000024	0.00000263	0.000000658	0.0000072	0.0000032	—	—	—
2	0.000074	0.000071	0.000097	0.000096	0.00000210	0.00000105	0.00000239	0.00000176	—	—	—
3	0.000122	0.000168	0.000147	0.000218	0.00000709	0.00000532	0.00000595	0.00000574	—	—	—
4	0.000186	0.000320	0.000201	0.000392	0.0000168	0.0000168	0.0000124	0.0000146	—	—	—
6	0.00037	0.00085	0.00032	0.00091	0.0000596	0.0000853	0.000039	0.000062	—	—	—
8	0.00067	0.00188	0.00047	0.00170	0.000140	0.0000279	0.000091	0.000187	—	—	—
10	0.00112	0.00365	0.00065	0.00281	0.000275	0.000679	0.0018	0.00452	—	—	—
15	0.0033	0.0135	0.00135	0.00765	0.00109	0.00374	0.0064	0.0233	—	—	—
20	0.0074	0.0395	0.00271	0.0174	0.00337	0.0138	0.0155	0.076	—	—	—
25	0.0137	0.092	0.00561	0.0373	0.00849	0.0423	0.0287	0.185	—	—	—
30	0.0212	0.182	0.0106	0.0071	0.0171	0.105	0.0442	0.368	—	—	—
40	0.038	0.048	0.266	0.256	0.0440	0.400	0.078	0.979	—	—	—
50	0.055	0.95	0.0489	0.633	0.0785	1.00	0.108	1.91	—	—	—
60	0.068	1.56	0.9724	1.238	0.115	1.97	0.133	3.12	—	—	—
70	0.079	2.29	0.094	2.07	0.152	3.31	0.151	4.54	—	—	—
80	0.088	3.12	0.114	3.11	0.188	5.01	0.166	6.13	—	—	—
90	0.094	4.02	0.132	4.34	0.224	7.06	0.177	7.85	—	—	—
100	0.100	5.01	0.147	5.74	0.259	9.47	0.187	9.67	—	—	—

SPECIFIC HEAT AND ENTHALPY OF SOME SOLIDS AT LOW TEMPERATURES (continued)

Sodium ^m			Tantalum			Tin (white)			Titanium		
T	C _p	H — H ₀	C _p	H — H ₀	C _p	H — H ₀	C _p	H — H ₀	C _p	H — H ₀	
°K	jg ⁻¹ deg ⁻¹ K	jg ⁻¹	jg ⁻¹ deg ⁻¹ K	jg ⁻¹	jg ⁻¹ deg ⁻¹	jg ⁻¹	jg ⁻¹ deg ⁻¹ K	jg ⁻¹	jg ⁻¹ deg ⁻¹ K	jg ⁻¹	
1	0.000081	0.000035	0.000032	0.000016	0.0000170	0.0000079	0.000071	0.000035	—	—	
2	—	—	0.000063 ^a	0.000021 ^a	0.0000041 ^a	0.0000099 ^a	—	—	—	—	
2	0.000289	0.000204	0.000068	0.000065	0.000047	0.0000383	0.000146	0.000143	—	—	
2	—	—	0.000054 ^a	0.000026 ^a	0.000048 ^a	0.0000228 ^a	—	—	—	—	
3	0.00076	0.00070	0.000112	0.000155	0.000109	0.000113	0.000226	0.000329	—	—	
3	—	—	0.000178 ^a	0.000138 ^a	0.000151 ^a	0.000116 ^a	—	—	—	—	
3.72 ⁿ	—	—	—	—	0.000198	0.000221	—	—	—	—	
3.72	—	—	—	—	0.000285 ^a	0.000270 ^a	—	—	—	—	
4	0.00160	0.00184	0.000171	0.000295	0.000245	0.000283	0.000317	0.000599	—	—	
4	—	—	0.000352 ^a	0.000400 ^a	—	—	—	—	—	—	
4.39 ^o	—	—	0.000201	0.000368	—	—	—	—	—	—	
4.39	—	—	0.000433 ^a	0.000553 ^a	—	—	—	—	—	—	
5	0.00298	0.00408	—	—	0.00054	0.00065	—	—	—	—	
6	0.0051	0.0081	0.000333	0.000776	0.00127	0.00151	0.00054	0.00145	—	—	
8	0.0122	0.0247	0.000648	0.00173	0.0042	0.0068	0.00084	0.00281	—	—	
10	0.0238	0.0602	0.00117	0.00352	0.0081	0.0190	0.00126	0.00489	—	—	
12	0.0397	0.123	—	—	—	—	—	—	—	—	
14	0.063	0.225	—	—	—	—	—	—	—	—	
15	—	—	0.00360	0.0145	0.226	0.093	0.0033	0.0156	—	—	
16	0.093	0.380	—	—	—	—	—	—	—	—	
18	0.124	0.597	—	—	—	—	—	—	—	—	
20	0.155	0.875	0.00823	0.0432	0.040	0.251	0.0070	0.040	—	—	
25	0.259	1.90	0.0153	0.102	0.058	0.498	0.0134	0.090	—	—	
30	0.364	3.45	0.0240	0.202	0.076	0.834	0.0245	0.182	—	—	
40	0.544	8.03	0.0430	0.540	0.106	1.75	0.0571	0.581	—	—	
50	0.695	14.2	0.0604	1.06	0.130	2.93	0.0992	1.358	—	—	
60	0.793	21.7	0.0754	1.74	0.148	4.33	0.1467	2.592	—	—	
70	0.86	30.0	0.0189	4.27	0.162	5.88	0.189	4.27	—	—	
80	0.91	38.9	0.0976	3.49	0.173	7.55	0.230	6.37	—	—	
90	0.95	48.2	0.105	4.50	0.182	9.33	0.267	8.86	—	—	
100	0.98	57.9	0.111	5.58	0.189	11.18	0.300	11.69	—	—	

Tungsten

Zinc

T	C _p	H — H ₀	C _p	H — H ₀
°K	jg ⁻¹ deg ⁻¹ K	jg ⁻¹	jg ⁻¹ deg ⁻¹ K	jg ⁻¹
1	0.000074	0.000037	0.000011	0.000005
2	0.0000158	0.0000152	0.000028	0.000023
3	0.0000262	0.0000360	0.000058	0.000065
4	0.0000393	0.0000685	0.00011	0.00014
6	0.0000783	0.000182	0.00029	0.00053
8	0.000141	0.000396	0.00096	0.0016
10	0.000234	0.000765	0.0025	0.0050
15	0.000725	0.00297	0.011	0.034
20	0.00189	0.00927	0.026	0.125
25	0.00421	0.0237	0.049	0.31
30	0.00783	0.0534	0.076	0.62
40	0.0184	0.181	0.125	1.62
50	0.0332	0.436	0.171	3.11
60	0.0483	0.843	0.208	5.01
70	0.0605	1.39	0.236	7.23
80	0.0715	2.05	0.258	9.70
90	0.0810	2.81	0.277	12.38
100	0.0888	3.66	0.293	15.24

^a Superconducting.

In germanium the electronic specific heat is markedly dependent on impurities. The values given are for pure germanium (negligible electronic specific heat).

^c α -Iron is the form that is thermodynamically stable at low temperatures. It has the body-centered cubic lattice which is the basis of the ferritic steels.

^d γ -Iron is stable between 910 and 1400°C. It has the face-centered cubic structure which is the basis of the austenitic steels. Since pure γ -iron is not stable at low temperatures the above values were calculated by application of the Kopp-Neumann rule to experimental data on two austenitic Fe-Mn alloys and are of uncertain accuracy.

^e Superconducting transition temperature.

ⁱ Superconducting transition temperature of mercury.

^j Melting temperature of mercury.

^l In silicon the electronic specific heat, γT , is markedly dependent on impurities. Values of the coefficient, γ_a , from zero to $2.4 \times 10^{-6} \text{ jg}^{-1} \text{ deg}^{-2}$ K have been reported. The values in the above table are for pure silicon ($\gamma = 0$).

^m It has been shown (Barrett 1956, Hull & Rosenberg 1959) that sodium partially transforms at low temperatures from the normal body-centered cubic structure to close-packed hexagonal. The transformation is of the martensitic type and is promoted by cold-working at the low temperatures. Inasmuch as none of the calorimetric measurements on sodium were accompanied by crystallographic analysis, the tabulated data below 100°K are to some degree ambiguous.

ⁿ Superconducting transition temperature of tin.

^o Superconducting transition temperature of tantalum.

CONSTANTS OF DEBYE-SOMMERFELD EQUATION

$C_v = \gamma T + \alpha T^3$; $\alpha = 12\pi^4 R / 50^3$; $0^\circ \leq T \leq T_{max}$; T_{max} = maximum temperature to which the equation can be used with the limiting value of θ .

Substance	$10^6\gamma$	γ	$10^6\alpha$	0°	T_{max}
Metals	$\text{Jg}^{-1} \text{deg}^{-2} \text{K}$	$\text{mJg-atom}^{-1} \text{deg}^{-2} \text{K}$	$\text{Jg}^{-1} \text{deg}^{-4} \text{K}$	deg K	deg K
Aluminum	50.4	1.36	0.93	425	4
Beryllium	25	0.226	0.138	1160	20
Bismuth	0.32	0.067	5.66	118	2
Cadmium	5.6	0.63	2.69	186	3
Chromium	28.3	1.47	0.165	610	4
Copper	10.81	0.687	0.746	344.5	10
Germanium ^a	—	—	0.528	370	2
Gold	3.75	0.74	2.19	165	15
Indium	15.8	1.81	13.1	109	2
α -Iron	90	5.0	0.349	464	10
Lead	15.1	3.1	10.6	96	4
Magnesium	54	1.32	1.19	406	4
α -Manganese	251	13.8	0.328	476	12
Molybdenum	23	2.18	0.238	440	4
Nickel	120	7.0	0.39	440	4
Niobium	85	7.9	0.64	320	1
Palladium	98	10.5	0.89	274	4
Platinum	34.1	6.7	0.72	240	3
Rhodium	48	4.9	0.173	478	4
Silicon ^a	—	—	0.263	640	4
Silver	5.65	0.610	1.58	225	4
Sodium ^a	60	1.37	21.4	158	4
Tantalum	31.5	5.7	0.69	250	4
Tin (white)	14.7	1.75	2.21	195	2
Titanium	71	3.4	0.54	420	10
Tungsten	7	1.3	0.16	405	4
Zinc	9.6	0.63	1.10	300	4
Alloys					
Constantan ^a	113	6.9	0.56	384	15
Monel ^a	108	6.5	0.62	374	20
Other inorganic substances					
Diamond	—	—	0.0152	2200	50
Ice	—	—	15.2	192	10
Pyrex	—	—	3.14	—	5
Organic substances					
Glyptal	—	—	27	—	4
Lucite	—	—	35	—	4
Polystyrene	—	—	63	—	4

^a Superconducting.

THERMAL PROPERTIES OF PURE METALS

From Handbook of Tables for Applied Engineering Science by R. E. Bolz and G. L. Tuve, The Chemical Rubber Co., 1970

Metal	At Atmospheric Pressure						Liquid Metal		
	At 100°K			At 25°C (77°F)			Vapor pressure		
	Latent heat of fusion, cal/g	Thermal conductivity, watts/cm°C	Specific heat, cal/g°C	Specific heat, cal/g°C	Coeff. of linear expansion, $(\times 10^{-6})$ $(^{\circ}\text{C})^{-1}$	Thermal conductivity, watts/cm²°C*	Specific heat (liquid) at 2000°K, cal/g°C	10^{-3} atm	10^{-6} atm
Aluminum	95	3.00	0.115	0.215	25	2.37	0.26	1,782	1,333
Antimony	38.5	—	0.040	0.050	9	0.185	0.062	1,007	741
Beryllium	324	—	0.049	0.436	12	2.18	0.78	1,793	1,347
Bismuth	12.4	—	0.026	0.030	13	0.084	0.036	1,155	851
Cadmium	13.2	1.03	0.047	0.055	30	0.93	0.063	655	486
Chromium	79	1.58	0.046	0.110	6	0.91	0.224	1,992	1,530
Cobalt	66	—	0.057	0.10	12	0.69	0.164	2,167	1,652
Copper	49	4.83	0.061	0.092	16.6	3.98	0.118	1,862	1,391
Gold	15	3.45	0.026	0.031	14.2	3.15	0.0355	2,023	1,510
Iridium	33	—	0.022	0.031	6	1.47	0.0434	3,253	2,515
Iron	65	1.32	0.052	0.108	12	0.803	0.197	2,093	1,594
Lead	5.5	0.396	0.028	0.031	29	0.346	0.033	1,230	889
Magnesium	88.0	1.69	0.016	0.243	25	1.59	0.32	857	638
Manganese	64	—	0.064	0.114	22	—	0.20	1,495	1,131
Mercury	2.7	—	0.029	0.033	—	0.0839	—	393	287
Molybdenum	69	1.79	0.033	0.060	5	1.4	0.089	3,344	2,558
Nickel	71	1.58	0.055	0.106	13	0.899	0.175	2,156	1,646
Niobium (Columbium)	68	0.552	0.045	0.064	7	0.52	0.083	3,523	2,721
Osmium	34	—	—	0.031	5	0.61	0.039	—	—
Platinum	24	0.79	0.024	0.032	9	0.73	0.043	2,817	2,155
Plutonium	3	—	0.019	0.032	54	0.08	0.041	2,200	1,596
Potassium	14.5	—	0.150	0.180	83	0.99	—	606	430
Rhodium	50	—	—	0.058	8	1.50	0.092	—	—
Selenium	16	—	—	0.077	37	0.005	—	—	—
Silicon	430	—	0.062	0.17	3	0.835	0.217	2,340	1,749
Silver	26.5	4.50	0.045	0.057	19	4.27	0.068	1,582	1,179
Sodium	27	—	0.234	0.293	70	1.34	—	701	504
Tantalum	41	0.592	0.026	0.034	6.5	0.54	0.040	3,959	3,052
Thorium	17	—	0.024	0.03	12	0.41	0.047	3,251	2,407
Tin	14.1	0.85	0.039	0.054	20	0.64	0.058	1,857	1,366
Titanium	100	0.312	0.072	0.125	8.5	0.2	0.188	2,405	1,827
Tungsten	46	2.35	0.021	0.032	4.5	1.78	0.040	4,139	3,228
Uranium	12	—	0.022	0.028	13.4	0.25	0.048	2,861	2,128
Vanadium	98	—	0.061	0.116	8	0.60	0.207	2,525	1,948
Zinc	27	1.32	0.063	0.093	35	1.15	—	752	559

* (watts/cm°C) \times 860.421 = Cal(gm hr⁻¹ cm⁻¹ °C⁻¹)
 (watts/cm°C) \times 57.818 = Btu hr⁻¹ ft⁻¹ °F.

THERMAL CONDUCTIVITY OF DIELECTRIC CRYSTALS

Name	Remarks	Conductivity mW·cm ⁻¹ ·K		Name	Remarks	Conductivity mW·cm ⁻¹ ·K	
		83 K	273 K			83 K	273 K
Marble	Small crystals, 99.9% CaCO ₃	42	33	90% KBr, 10% KCl	Do	50	29
Do	99.99% CaCO ₃	54	38	75% KBr, 25% KCl	Do	29	21
Do	Large crystals	50	33	50% KBr, 50% KCl	Do	25	25
Calcite	Main crystal axis perpendicular to rod axis	180	46	25% KBr, 75% KCl	Pressed at 8000 atm	46	33
Do	Main crystal axis parallel to rod axis	293	54	10% KBr, 90% KCl	Do	80	50
Sylvite	Natural crystal	159	75	50% KCl, 50% NaCl	Do	188	71
KCl	Pressed at 8000 atm	314	88	KNO ₃	Do	17	21
KCl	From a melt	402	92	Mercuric chloride	Do	109	25
NaCl	Do	343	92	NH ₄ Cl	Do	67	25
NaCl	Pressed at 8000 atm	251	71	NH ₂ Br	Do	33	13
Rock salt	Do	180	63	Ba(NO ₃) ₂	Do	29	21
Sylvite	Do	343	84	Copper sulfate	Do	25	25
KCl	Pressed at 1250 atm	243	75	Magnesium sulfate	Do	17	17
KCl	Pressed at 2500 atm	368	92	K ₃ Fe(CN) ₆	Do	13	21
KCl	Pressed at 8900 atm	402	96	Chrom alum	Do	13	21
KBr	Pressed at 8000 atm	92	38	Potassium alum	Do	17	21
NaBr	Do	50	25	Potassium bichromate	Main crystal axis perpendicular to rod axis	17	17
KI	Do	121	29	Do	Main crystal axis parallel to rod axis	234	264
KF	Do	234	71	Topaz	Mineral	63	84
NaF	Do	519	105	Zincblende	Do	88	46
RbI	Do	59	33	Beryl	Do	38	46
RbCl	Do	29	21	Tourmaline	Do	—	—

THERMAL CONDUCTIVITY OF CERTAIN METALS

From NSRDS-NBS 8

R. W. Powell, C. Y. Ho, and P. E. Liley

The thermal conductivity, k , is given in the units $\text{W}\cdot\text{cm}^{-2}\cdot\text{K}^{-1}$.

To convert to $\text{cal}\cdot\text{cm}^{-2}\cdot\text{h}^{-1}\cdot\text{K}^{-1}$ multiply the values listed in the tables by 860.421.

To convert to $\text{Btu}\cdot\text{ft}^{-2}\cdot\text{h}^{-1}\cdot\text{F}^{-1}$ multiply the values listed in the tables by 57.818.

ρ_0 is the residual electrical resistivity and the value of ρ at 4.2°K is used approximately as ρ_0 .

T, K	Aluminum	Copper	Gold	Iron	Manganin	Platinum	Silver	Tungsten
	99.996+% $\rho_0 = 0.00315$	99.999+% $\rho_0 = 0.000851$	99.999+% $\rho_0 = 0.0055$	99.998+% $\rho_0 = 0.0327$	99.999% $\rho_0 = 0.0106$	99.999% $\rho_0 = 0.00062$	99.999+% $\rho_0 = 0.0017$	
μohm cm	μohm cm	μohm cm	μohm cm	μohm cm	μohm cm	μohm cm	μohm cm	
0	0	0	0	0	0	0	0	0
1	7.8	28.7	4.4	0.75	0.0007	2.31	39.4	14.4
2	15.5	57.3	8.9	1.49	0.0018	4.60	78.3	28.7
3	23.2	85.5	13.1	2.24	0.0031	6.79	115	42.6
4	30.8	113	17.1	2.97	0.0046	8.8	147	55.6
5	38.1	138	20.7	3.71	0.0062	10.5	172	67.1
6	45.1	159	23.7	4.42	0.0078	11.8	187	76.2
7	51.5	177	26.0	5.13	0.0095	12.6	193	82.4
8	57.3	189	27.5	5.80	0.0111	12.9	190	85.3
9	62.2	195	28.2	6.45	0.0128	12.8	181	85.1
10	66.1	196	28.2	7.05	0.0145	12.3	168	82.4
11	69.0	193	27.7	7.62	0.0162	11.7	154	77.9
12	70.8	185	26.7	8.13	0.0180	10.9	139	72.4
13	71.5	176	25.5	8.58	0.0197	10.1	124	66.4
14	71.3	166	24.1	8.97	0.0215	9.3	109	60.4
15	70.2	156	22.6	9.30	0.0232	8.4	96	54.8
16	68.4	145	20.9	9.56	0.0250	7.6	85	49.3
18	63.5	124	17.7	9.88	0.0285	6.1	66	40.0
20	56.5	105	15.0	9.97	0.0322	4.9	51	32.6
25	40.0	68	10.2	9.36	0.0410	3.15	29.5	20.4
30	28.5	43	7.6	8.14	0.0497	2.28	19.3	13.1
35	21.0	29	6.1	6.81	0.0583	1.80	13.7	8.9
40	16.0	20.5	5.2	5.55	0.067	1.51	10.5	6.5
45	12.5	15.3	4.6	4.50	0.075	1.32	8.4	5.07
50	10.0	12.2	4.2	3.72	0.082	1.18	7.0	4.17
60	6.7	8.5	3.8	2.65	0.097	1.01	5.5	3.18
70	5.0	6.7	3.58	2.04	0.110	0.90	4.97	2.76
80	4.0	5.7	3.52	1.68	0.120	0.84	4.71	2.56
90	3.4	5.14	3.48	1.46	0.127	0.81	4.60	2.44
100	3.0	4.83	3.45	1.32	0.133	0.79	4.50	2.35
150	2.47	4.28	3.35	1.04	0.156	0.762	4.32	2.10
200	2.37	4.13	3.27	0.94	0.172	0.748	4.30	1.97
250	2.35	4.04	3.20	0.865	0.193	0.737	4.28	1.86
273	2.36	4.01	3.18	0.835	0.206	0.734	4.28	1.82
300	2.37	3.98	3.15	0.803	0.222	0.730	4.27	1.78
350	2.40	3.94	3.13	0.744	0.250	0.726	4.24	1.70
400	2.40	3.92	3.12	0.694	(0.279)	0.722	4.20	1.62
500	2.37	3.88	3.09	0.613	(0.338)	0.719	4.13	1.49
600	2.32	3.83	3.04	0.547	(0.397)	0.720	4.05	1.39
700	2.26	3.77	2.98	0.487		0.723	3.97	1.33
800	2.20	3.71	2.92	0.433		0.729	3.89	1.28
900	2.13	3.64	2.85	0.380		0.737	3.82	1.24
1000	[0.93]**	3.57	(2.78)	0.326		0.748	(3.74)	1.21
1100	[0.96]	3.50	(2.71)	0.297		0.760	(3.66)	1.18
1200	[0.99]	3.42	(2.62)	0.282		0.775	(3.58)	1.15
1300	[1.02]	(3.34)†	(2.51)	0.299		0.791		1.13
1400				0.309		0.807		1.11
1500				0.318		0.824		1.09
1600				(0.327)		0.842		1.07
						0.860		1.05
						0.877		1.03
						(0.895)		1.02
						(0.913)		1.00
								0.98
								0.96
								0.94
								0.925
								0.915
								0.905
								0.900
								(0.895)

* In the table the third significant figure is given only for the purpose of comparison and is not indicative of the degree of accuracy.

** Values in square brackets are for liquid state.

† Values in parentheses are extrapolated.

‡ Estimated.